


AD-A104 419 EFFECT OF SIDECCHAIN LENGTH AND CROSSLINKING ON IONIC 1/1  
CONDUCTIVITY IN POLY. (U) NORTHWESTERN UNIV EVANSTON IL  
DEPT OF CHEMISTRY J S TONGE ET AL. 24 AUG 87 016  
UNCLASSIFIED N00014-80-C-0532 F/G 7/4 NL



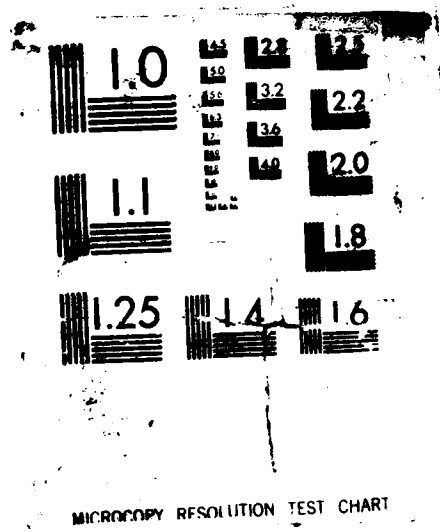

AD-A184 419

FILE COPY

(12)

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 016	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Effect of Sidechain Length and Crosslinking on Ionic Conductivity.		5. TYPE OF REPORT & PERIOD COVERED Interim Technical Report
7. AUTHOR(s) J. S. Tonge, P. L. Blonsky, D. F. Shriver, H. R. Allcock, P. A. Austin, T. X. Neenan and J. T. Sksko		6. PERFORMING ORG. REPORT NUMBER
3. PERFORMING ORGANIZATION NAME AND ADDRESS Northwestern University Dept. of Chemistry Department of Chemistry The Pennsylvania State Evanston, IL 60201 University Park, PA		8. CONTRACT OR GRANT NUMBER(s) N00014-80-C-0532
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Department of the Navy Arlington, Virginia 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 359-746
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE August 24, 1987
		13. NUMBER OF PAGES 1
		15. SECURITY CLASS. (of this report)
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report)  Approved for public release and sale. Distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES  Submitted to <u>Electrochem. Society</u> for publication.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)  polymer electrolytes, polyethyleneimine, polymer salt complexes, ionic conductivity, polyphosphazene-poly(ethylene glycol) copolymer		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)  A series of fully substituted poly(phosphazenes) with alkoxy sidechains, and/or dialkoxy crosslinks were synthesized and investigated as electrolyte host materials. All of the polymers readily formed complexes with $\text{LiSO}_3\text{CF}_3$ , $\text{LiSO}_3\text{C}_2\text{F}_5$ and $\text{Li}_2(\text{SO}_3)_2\text{C}_2\text{F}_5$ . The polymer with seven ether oxygens in its sidechain gives the highest conducting polymer salt complex at 30 °C. The crosslinked polymers were found to be totally amorphous with comparable conductivity and increased resistance to flow at elevated temperatures.		

DTIC  
ELECTE  
SEP 04 1987  
S D  
C6 E

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

6 9 1 052

# Effect of Sidechain Length and Crosslinking on Ionic Conductivity in Polyphosphazene Solid Electrolytes.

J. S. Tonge, P. M. Blonsky\* and D. F. Shriver.  
Department of Chemistry and Materials Research Center  
Northwestern University, Evanston, Illinois 60201  
H. R. Allcock, P. E. Austin<sup>§</sup>, T. X. Neenan and  
J. T. Sisko Department of Chemistry, The Pennsylvania  
State University, University Park, Pennsylvania  
16802

\* Current Address: Union Carbide Corp.,  
Westlake, Ohio

§ Current Address: Union Carbide Corp.,  
Tarrytown, New York

## INTRODUCTION

The use of ethylene oxide ( $\text{CH}_2\text{CH}_2\text{O}$ ) main and side chain polymers with alkali metal salts as solvent-free polymer electrolytes has developed from the parent Polyethylene oxide (PEO)<sup>1</sup> to the more exotic and highly conducting Poly(bis(2-(2-methoxyethoxy)ethoxy)phosphazene (MEEP).<sup>2,3</sup> We report here the thermal, ac and dc conductivity, and x-ray diffraction properties of a new class of polyphosphazenes that possess polyether side groups linked to the flexible inorganic backbone. Also details of the initial study on the effect of crosslinking MEEP with Poly(ethylene glycol), (PEG), on the ionic conductivity and mechanical properties are presented.

## NOMENCLATURE

A series of fully substituted poly(alkoxyphosphazenes),  $(\text{NP}[\text{O}(\text{C}_2\text{H}_4\text{O})_X\text{CH}_3]_2)_n$  ( $n \geq 15,000$  and  $X = 1, 2, 7, 12, 17$ ) along with MEEP ( $X = 2$ ) crosslinked with PEG (mol wt. 1000) were synthesized.<sup>4</sup> A systematic nomenclature based on the number  $X$ , of ethoxy groups in the sidechains is employed in this work, (MEX-P), eg. for both side chains  $X = 7$  we write ME7P. For the mixed substituent polymers, we use ME(X/X')P(A,B) where A and B denote the relative percentage of X and X' respectively eg. ME2/12P (50,50) which is a 50:50 mixture of  $X = 2$  and  $X = 12$  sidechains.

## RESULTS

All the polymers synthesized formed complexes with the following lithium polyfluoro-sulphonic acid salts:  $\text{LiSO}_3\text{CF}_3$ ,  $\text{LiSO}_3\text{C}_6\text{F}_9$  and  $\text{Li}_2(\text{SO}_3)_2\text{C}_2\text{F}_2$ .

Previously,<sup>5</sup> it was found that a ratio of sixteen ether oxygens to one lithium ion gave the highest conducting MEEP complexes (the oxygen in the P-O-CH<sub>2</sub> link is not included in this count). This stoichiometry was again found to give the optimum conductivity with the new polyphosphazenes.

The highest conducting polymer salt complexes were found to be amorphous at room temperature by DSC and x-ray diffraction. Only the ME12P and ME17P polymer salt complexes showed low melting complexes at +5 and +15°C respectively.

The ionic conductivity was determined by complex impedance measurements using Platinum, ion blocking, electrodes. Figure 1 gives the conductivity of the polymer salt complexes at the optimum stoichiometry of sixteen ether oxygens to one lithium ion. The figure also includes the glass transition temperature,  $T_g$ , of the pure polymers. Plots of  $\ln(\sigma T^{1/2})$  or  $\ln(\sigma)$  versus  $1/T$  gave a gentle curve similar to those observed for MEEP complexes.

In the crosslinked polymer salt complexes there is a significant reduction in flow at temperatures above 70°C, with only a small reduction in conductivity compared to uncrosslinked MEEP complexes.

## CONCLUSION

The highest room temperature conductivity was reached for ME7P ( $5 \times 10^{-5} \Omega^{-1}\text{cm}^{-1}$ ); this is the highest known for any solvent-free polymer electrolyte. Polymers with sidechain lengths of  $X = 7$  to 12 seem to represent an optimum between lower  $T_g$  and a less effective "hand to hand" ion transport mechanism.

The polyphosphazenes with their ease of substitution continue to provide an array of polymers suitable as electrolyte host materials.

## REFERENCES

1. P. V. Wright. *Br. Polymer J.* **7**, 319 (1975).
2. P. M. Blonsky, D. F. Shriver, P. E. Austin and H. R. Allcock. *J. Amer. Chem. Soc.* **106**, 6854 (1984).
3. P. M. Blonsky, D. F. Shriver, P. E. Austin and H. R. Allcock. *Solid State Ionics* **18 and 19**, 258 (1986).
4. H. R. Allcock, P. E. Austin, T. X. Neenan, J. T. Sisko, P. M. Blonsky and D. F. Shriver *Macromolecules* in press.
5. P. M. Blonsky, Thesis, 1986, Northwestern University

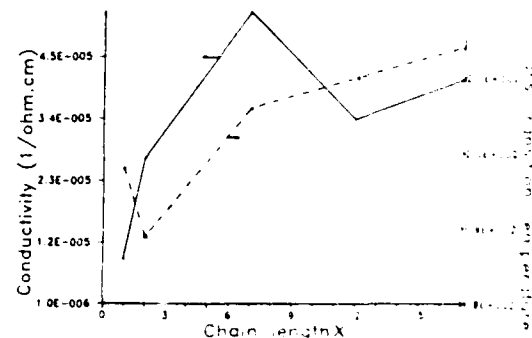


Figure 1. The variation of the optimum ionic conductivity (—) and glass transition temperature (pure polymers, ---) with sidechain length  $X$  at 30°C.



Accession For	
NTIS GSA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input checked="" type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Special
A-1	

END

10-87

DTIC